

Indetex nv
Rue du Mont Gallois 58
7700 MOUSCRON

Your notice of
07-11-2023

Your reference

Date
15-11-2023

Analysis Report 23.05976.02

Required tests :

EN 13773 (2003)

Sample id	Information given by the client	Date of receipt
T2325244	BIELLA	07-11-2023


Gina Créelle
Order responsible


This report may be reproduced, as long as it is presented in its entire form, without written permission of Centexbel.
The results of the analysis cover the received samples. Centexbel is not responsible for the representativeness of the samples.
In assessing compliance with the specifications, we did not take into account the uncertainty on the test results.



Samples

T2325244
BIELLA

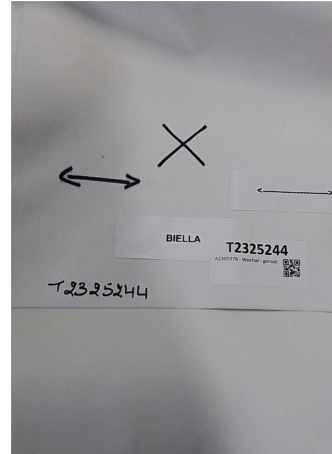




Reference: T2325244 - BIELLA

Washing and drying

Date of ending the test	08-11-2023
Standard used	ISO 6330 (2000) + A1 (2008), ISO 6330 (2012)
Deviation from the standard	-
Conditioning	20°C, relative humidity 65%
Apparatus	Wascator FOM 71 (type A)
Used detergent	ECE detergent (Type 3)
Washing method and temperature	8A- 30°C (2000)
Drying method	A = Line dry (2000)
Number of washing cycles	2
Mass of the test specimens	1780g
Mass of the ballast	The washing machine is filled with ballast to achieve 2 kg in total
Remark	Washing always occurs with a ballast type III 100% PES regardless of the composition of the fabric.

Sample generated: T2325244_01d



Reference: T2325244_01d - BIELLA

Textiles – Burning behaviour – Curtains and drapes - Textile fabrics - Determination of the ignitability of vertically oriented specimens.

Date of ending the test 15-11-2023
 Standard used EN 1101 (1995) + A1 (2005)
 Product standard EN 13773 (2003)

Deviation from the standard -

Conditioning 20°C, relative humidity 65%
 Testing atmosphere 21°C, relative humidity 52%

Ignition Bottom edge

The test specimens have been washed 2 times instead of 12 times.

Length

Flame application time (s)	Cases of ignition	Cases of non-ignition
1	0	1
2	0	1
3	0	1
4	0	1
5	0	1
10	0	1
15	0	1
20	0	5

The mean of the recorded times at which ignition was observed is calculated

No ignition within 20 s

**Width**

Flame application time (s)	Cases of ignition	Cases of non-ignition
1	0	1
2	0	1
3	0	1
4	0	1
5	0	1
10	0	1
15	0	1
20	0	5

The mean of the recorded times at which ignition was observed is calculated
No ignition within 20 s

Reference: T2325244_01d - BIELLA

Textiles and textile products – Burning behaviour – Curtains and drapes. Measurement of flame spread of vertically oriented specimens with large ignition source.

Date of ending the test 15-11-2023
Standard used EN 13772 (2011)
Product standard EN 13773 (2003)

Deviation from the standard -

Conditioning 20°C, relative humidity 65%

The test specimens have been washed 2 times instead of 12 times.

Length

	Front	Back	Back	Back
Severance 1 st thread	no	no	no	yes
Severance 2 nd thread	no	no	no	no
Severance 3 rd thread	no	no	no	no
Time to sever 3 rd thread (s)	/	/	/	/
Destroyed length (mm)	120	165	150	150
Flaming debris	no	no	no	no

Width

	Front	Back	Front	Front
Severance 1 st thread	no	no	no	no
Severance 2 nd thread	no	no	no	no
Severance 3 rd thread	no	no	no	no
Time to sever 3 rd thread (s)	/	/	/	/
Destroyed length (mm)	105	90	125	115
Flaming debris	no	no	no	no



Additional tests

Length

	Back	Back	Back
Severance 1 st thread	no	no	no
Severance 2 nd thread	no	no	no
Severance 3 rd thread	no	no	no
Time to sever 3 rd thread (s)	/	/	/
Destroyed length (mm)	125	145	135
Flaming debris	no	no	no

**Classification in accordance with EN
13773**

Class 1